

## 2-Face Viewable Display Using Dye-Doped Liquid Crystal

Chao Ping Chen\*, Hongjing Li\*, Zhenghong He\*, Xiao Li\*, Yuan Xiong\*, Wei Hu\*, Yikai Su\*, and Chul Gyu Jhun\*\*

\*National Engineering Lab of TFT-LCD Materials and Technologies, Department of Electronic Engineering, Shanghai Jiao Tong University, Shanghai, China

\*\*Department of Optoelectronics Display Engineering, Hoseo University, Asan, Korea

### Abstract

We present a liquid crystal display that allows two faces of the display viewed at opposite directions to show different image/video content simultaneously. This device is characterized by a dye-doped liquid crystal, which can eliminate the need for polarizers and offer a very low crosstalk between two separated viewing angles.

### Keywords

multi-view; 2-face viewable; liquid crystal; dye-doped; multi-domain; low crosstalk

### 1. Introduction

2-face viewable liquid crystal display (LCD) devices [1-4] are an ingenious solution that accommodates two distinct viewing cones together in one display. As with multiple viewing angles, different image or video contents can be displayed simultaneously on a screen depending on the viewing direction. Courtesy of this franchise, this technology offers many possibilities that were previously not possible or at least difficult. Picture two persons sitting in a car. One could observe the global positioning system (GPS) map on the navigator from driver's seat, whereas the other could enjoy a soap opera from passenger's seat. Likewise, signages in public places become able to showcase more than one advertisement as a person goes by.

To date, only a few viable solutions have been proposed for this use. Parallax barrier, adopted in Sharp's proprietary three-way viewing-angle LCD [5], and lenticular lenses [6] are the commonly used physical means to route light from the subpixels to each independent field of view. However, both of them indeed demand an add-on device to assist a major LCD panel in order to fulfill their function. This inevitably will be accompanied by a sophisticated process of production, resulting in a decrease in the yield. Besides, a noticeably raised cost due to the parallax barrier or lenticular lens would not appeal to many manufacturers and consumers. Another approach to achieve multiple viewing angles is known as the vector error diffusion [7], a halftoning method. Since this method involves the signal processing in imaging, the output multi-view effect is very limited and problematic.

### 2. Principle of Guest-Host LC

Guest-host (GH) LC, best known for its application in the polarizer-free displays [8], is a mixture acquired by doping a host LC with a few percent (1-5 wt%) of guest dichroic dye. The impressive ability of dichroic dye to absorb light strongly along the principal molecule axis, that is, the absorption axis (AA), and to transmit light easily along the perpendicular direction lends itself to modulating the light intensity. By invoking the Beer-Lambert law [9], under the condition of a dilute solution,

the normalized transmittance of a homogeneous GH cell can be given by

$$T_{\parallel} = \exp(-\alpha_{\parallel}cd), \quad (1)$$

$$T_{\perp} = \exp(-\alpha_{\perp}cd), \quad (2)$$

where  $T_{\parallel,\perp}$  and  $\alpha_{\parallel,\perp}$  represent the transmittance and absorptivity (the absorption coefficients) parallel and perpendicular to the incident plane of the light, characteristic of the material, respectively,  $c$  is the dye concentration and  $d$  is the cell gap. The dichroic ratio (DR), a measure of the dye's absorptive anisotropy, is defined as

$$DR = \frac{\alpha_{\parallel}}{\alpha_{\perp}}. \quad (3)$$

Referring to Fig. 1, once LC and dye materials are blended together, the movement of dye molecules will follow that of LC directors in a sense that their optical axes always align in a line. In this regard, only the LC director is shown to represent the LC-dye mixture as a unity. When in the off-state, that is no external voltage being applied, assume that LC and dye are together positioned at a certain angle. The incoming unpolarized light is incident from the directions indicated by the wavevectors  $k$  at normal and  $k'$  at oblique. Thereafter, the p-(parallel) and s-(perpendicular) wave components of incident light will be converted into as E-wave and O-wave, respectively, upon entering into the anisotropic medium of LC-dye mixture. For every incident direction, the s-wave is going to experience pronounced attenuation brought by the O-wave absorption nature of E-type dye, as the s-wave is all the time orthogonal to the dye's optical axis. The p-wave, on the other hand, is to be more or less transmitted as long as there is a non-zero portion of E-wave component after its conversion. In particular, when the incident direction of wavevector is normal to the LC director, a maximum transmittance of p-wave will be acquired.

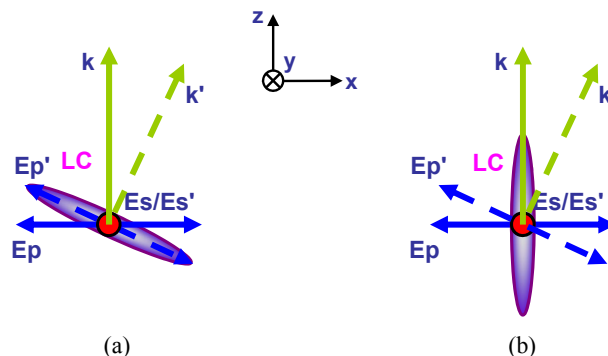


Figure 1. Principle of light absorption of E-type dye when in the off-state and (b) on-state.



5. Results and Discussion

We shall mention that the following results are all calculated merely with right-view pixel, while the left one is omitted for the sake of clarity. Figures 4(a) and 4(b) are graphs showing the voltage-transmittance (V-T) curve for an LC-dye layer with cellgaps of 3 and 8 μm, respectively. These curves are observed for viewing directions of 0° (front), +45° (45° on the right), and -45° (45° on the left), of which, the +45° direction demonstrates a continuous change from the maximum to the minimum transmittance. This is in an agreement with the statement earlier discussed. By comparing the V-T curves of +45° and -45°, it also can be said that the present invention is free of crosstalk [14], as the light emitted from the opposite direction (-45°) is far below the level of viewable direction (+45°). Technically, this is quite advantageous to be applied as a multi-face viewable display device. Table 2 summarizes the figure of merits with respect to the six different cellgap conditions from 3 to 8 μm. As can be told, the large the cellgap, the better the CR as well as crosstalk. The selection of cellgap for a real device should depend on the actual physical properties of E-type dye and also on the performance requirement.

Figures 5(a) to 5(f) are a series of iso-luminance contours showing how the luminance changes in response to the variation of an applied voltage, when the LC-dye layer has a cellgap of 6 μm. At 0 V, the bright state or the maximum brightness is obtained and its area is primarily limited to the right half of the entire viewing cone, as expected. With an increase in the voltage, both the level and area of luminance are gradually scaling down to a dark state at 8 V.

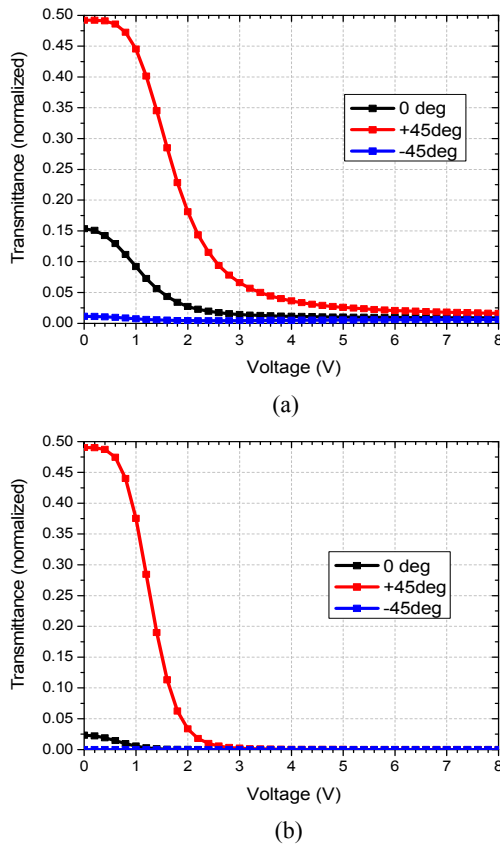


Figure 4. V-T curves for cellgaps of (a) 3 μm and (b) 8 μm.

Table 2. Figure of merits with respect to different cellgaps.

	d=3μm	d=4μm	d=5μm	d=6μm	d=7μm	d=8μm
T(0V)@+45°	0.4919	0.4905	0.4902	0.4902	0.4902	0.4902
T(8V)@+45°	0.01626	0.004777	0.001437	0.000438	0.000135	4.15E-05
T(0V)@-45°	0.01124	0.002837	0.000733	0.000192	5.09E-05	1.35E-05
T(8V)@-45°	0.006394	0.001269	0.000255	5.18E-05	1.06E-05	2.19E-06
Crosstalk(0V)	2.3%	0.6%	0.1%	0.0%	0.0%	0.0%
Crosstalk(8V)	39.3%	26.6%	17.7%	11.8%	7.9%	5.3%
CR@+45°	30.3	102.7	341.1	1119	3631	11812

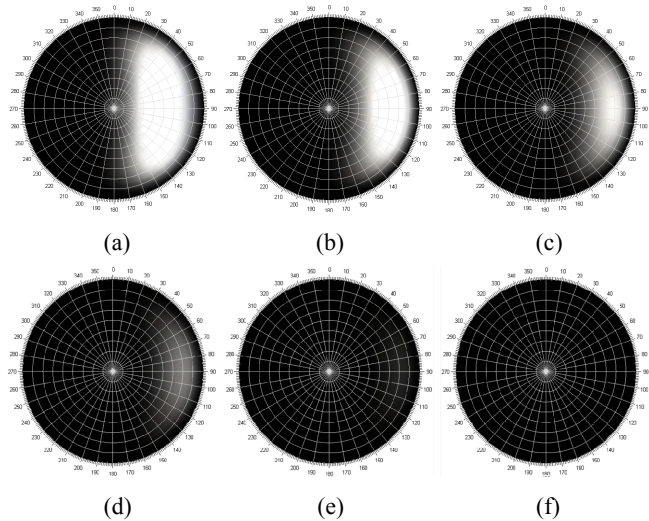


Figure 5. Iso-luminance contours of a dye-doped LC cell of 6 μm at voltages of (a) 0, (b) 1.2, (c) 1.6, (d) 2.0, (e) 2.6, and (f) 8.0 V.

As shown in Fig. 6, three contours compare the CRs of three different cellgaps (3, 4, and 8 μm), from which, it can be seen that high levels of CR are mainly confined to the right half of the entire viewing cone. Moreover, the best viewing direction for right-view pixels will be at 45° as it is optimized. Even though CRs over 5:1 can intrude some of the left half region, the transmittance level is still way too low to display any discernible information.

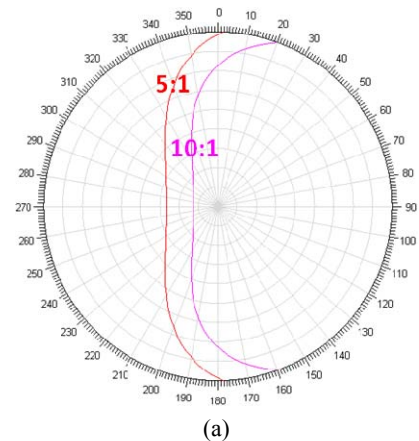
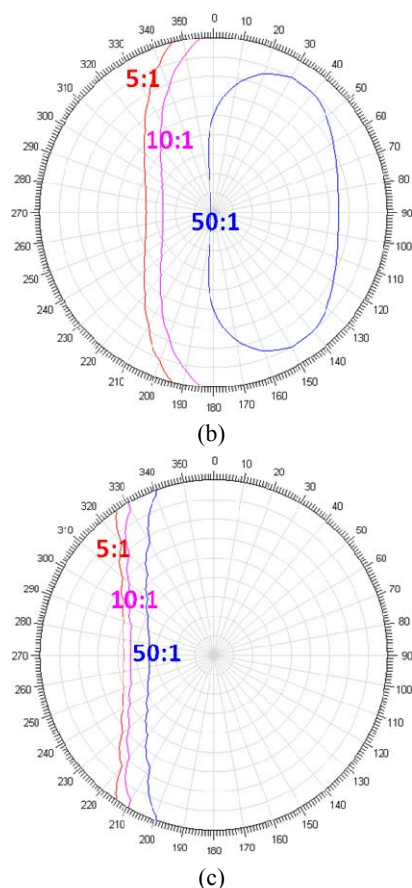


Figure 6a



**Figure 6.** Iso-CR contours of a dye-doped LC cell with the cellgaps of (a) 3  $\mu\text{m}$  and (b) 4  $\mu\text{m}$ , and (c) 8  $\mu\text{m}$ .

## 6. Conclusions

In conclusion, we have demonstrated a 2-face viewable LCD device that is capable of allowing simultaneous displays of two independent image or video contents on the same screen. The proposed structure features a multi-domain dye-doped LC cell, which in its own right can eliminate the use of polarizers. Incidentally, we have found out that E-type dye outrivals O-type dye in terms of the viewing angle splitting [15]. This device is typically useful for the application as digital signages, not only for its unique function but also for its competitive manufacturing cost.

## 7. Acknowledgements

This work is sponsored by 973 Program (2013CB328804), National Natural Science Foundation of China (61275026), Science and Technology Commission of Shanghai Municipality (11JC1405300), Shanghai Shuguang program (09SG13), and Fundamental Research Funds for the Central Universities (XDJK2011C047).

## 8. References

- [1] C.P. Chen, J.H. Lee, T.-H. Yoon, and J.C. Kim, "Monoview/Dual-View Switchable Liquid Crystal Display," *Opt. Lett.* **34**, 2222-2224 (2009).
- [2] C.P. Chen, T.-C. Chung, X. Guo, and Y. Su, "2-Face Viewable Liquid Crystal Display by In-Plane Switching," *Mol. Cryst. Liq. Cryst.* **544**, 232-236 (2011).
- [3] C.P. Chen, T.-C. Chung, and T.-S. Jen, "2-face viewable liquid crystal display using 2-domain vertically aligned cell," *Phot. Lett. Poland* **3**, 23-25 (2011).
- [4] C.P. Chen, X. Guo, Y. Su, T.-C. Chung, and T.-S. Jen, "A Mono/Dual-View Switchable LCD", *SID Symposium* **42**, pp. 1707-1710 (2011).
- [5] D.J. Montgomery and M. Khazova, "Method of Making a Parallax Barrier, Parallax Barrier and Autostereoscopic Display", *US patent* 6859256, (2005).
- [6] M.P.C.M. Krijn, S.T. de Zwart, D.K.G. de Boer, O.H. Willemsen, and M. Sluijter, "2-D/3-D Displays Based on Switchable Lenticulars", *J. Soc. Inf. Disp.* **16**, 847-855 (2008).
- [7] C.W. Wu, "Multiple images viewable on twisted-nematic mode liquid-crystal displays," *IEEE Signal Proc. Lett.* **10**, 225-227 (2003).
- [8] H.S. Cole and R.A. Kashnow, "A new reflective dichroic liquid crystal display device," *Appl. Phys. Lett.* **30**, 619 (1977).
- [9] S.-T. Wu and D.K. Yang, *Reflective liquid crystal displays*, (Wiley, Hoboken, NJ, 2001), Chap. 6.
- [10] C.G. Jhun, C.P. Chen, T.-H. Yoon, and J.C. Kim, "Multidomain Structure for Infinite Memory Time of Bistable Chiral Splay Nematic Liquid Crystal Device," *Jpn. J. Appl. Phys.* **45**, 5117-5120 (2006).
- [11] J.-H. Seo, S.P. Lee, T.-H. Yoon, and J.C. Kim, "Anisotropy-Enhanced Polyimidization by Pre-Irradiation of Ion Beam on Polyamic Acid for Liquid Crystal Alignment," *Jpn. J. Appl. Phys.* **46**, 6057-6061 (2007).
- [12] M. Schadt, K. Schmitt, V. Kozenkov, and V. Chigrinov, "Surface-induced parallel alignment of liquid crystals by linearly polymerized photopolymers," *Jpn. J. Appl. Phys.* **31**, 2155-2164 (1992).
- [13] V. Chigrinov, E. Prudnikova, K.W. Ng, and H.S. Kwok, "Non Polarizer Guest-Host mode based on Dyes with Negative Dichroism," *Jpn. J. Appl. Phys.* **42**, 1297-1300 (2003).
- [14] Y.-J. Wu, Y.-S. Jeng, P.-C. Yeh, C.-J. Hu, and W.-M. Huang, "Stereoscopic 3D Display Using Patterned Retarder," *SID Symposium* **39**, 260-263 (2008).
- [15] C.P. Chen, K.-H. Kim, T.-H. Yoon, J.C. Kim, "A Viewing Angle Switching Panel Using Guest-Host Liquid Crystal," *Jpn. J. Appl. Phys.* **48**, 062401-1-7 (2009).